




CARPATHIAN JOURNAL OF FOOD SCIENCE AND TECHNOLOGY

Vol.14(4)
2022

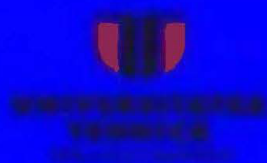

Technical University of Cluj Napoca
U.T.Press Publishing House



Carpathian Journal of Food Science and Technology

Print : ISSN 2066-6845
Online : ISSN 2344-5459
ISSN-L 2066-6845

Vol. 14, Nr.(4) 2022



Editor in Chief:

Liviu Giurgiulescu -Technical University of Cluj Napoca, North University Center of Baia Mare, Chemistry-Biology Department, giurgiulescu@yahoo.com

Executive-editor:

NG EYK ,School of Mechanical & Aerospace Engineering, Nanyang Technological University N3.2-02-70, 50 Nanyang Avenue, Singapore 639798, MYKNG@ntu.edu.sg

Permanent Editors Number 13(2) 2021

Anca Peter- Technical University of Cluj Napoca, North University Center of Baia Mare, peteranca@yahoo.com

Professor Mohammed Kuddus ,Department of Biochemistry, College of Medicine,University of Hail, Hail,Kingdom of Saudi Arabia, mkuddus@gmail.com

Professor Luiz Gustavo Lacerda ,State University of Ponta Grossa Department of Food Engineering, Ponta Grossa, PR - Brazil, luizgustavo75@gmail.com

Editorial board:

Prof. dr. Michael Eskin,University of Manitoba, Canada

Prof.dr. Vizireanu Camelia - University of Galați, Faculty of Food Science and Engineering, Romania

Prof.dr. Chifiriuc Mariana Carmen - University of Bucharest, Faculty of Biology, Romania

Prof.dr. Trașcă Teodor - USAMV of Banat, Timisoara, Romania

Dr. Qian Lu-College of Food, Agricultural and Natural Resources Sciences, University of

Minnesota,USA Prof.dr. Monye Felicia Nwanne- University of Nigeria, Faculty of Law, Nigeria

Prof. dr.Jan Bojkovski - Faculty of Veterinary Medicine – University of Belgrade, Serbia

Dr. Poorna CR Yalagala, Department of Medicine,Diabetes & Metabolism, University of Illinois at Chicago, 60612, USA

Prof.dr. Vagelas Ioannis -Technological Institute of Larissa, TEI, Departament of Crop Protection and Plant Pathology, Greece

Prof. Dr. Claudio De Pasquale,Department Scienze Agrarie, Alimentari e Forestali, Università degli Studi di PALERMO, Italy

Prof.dr. Gerhard Schleining,Department of Food Sciences and Technology BOKU - University of Natural Resources and Life Sciences, Secretary General of the ISEKI-Food Association, Vienna, Austria

Technical University of Cluj Napoca, Romania
U.T. Press Publishing House



CONTENT

- Nameer Khairullah Mohammed, Wan Hasyera Wan Omar, Anis Shobirin Meor Hussin; *FORMULATION OF NATURAL HYDROCOLLOIDS AND VIRGIN COCONUT OIL AS A PLANT-BASED SALAD DRESSING*** **5-16**
- Mohammed Tahar Boubezari , Amina Bouchefra, Samir Djemai; *CHANGES IN PHYSICO-CHEMICAL PARAMETERS, BIOACTIVE COMPOUNDS AND SURVIVAL OF *Lactiplantibacillus plantarum* J12 IN FERMENTED CARROT JUICE*** **17-27**
- Martina Pencheva, Zhana Petkova, Ivayla Dincheva, Iliana Kostova, Stanka Damyanova, Albena Stoyanova, Liviu Gaceu; *PHYTOCHEMICAL AND BIOLOGICAL PROFILES OF FENNEL FRUITS (FOENICULUM VULGARE MILL. VAR. DULCE MILL.)*** **28-49**
- Nor Hayati Ibrahim, Tengku Nur Dayana Tengku Zakaria, Yusnita Hamzah, Wan Rosli Wan Ishak, Amiza Mat Amin; *EFFECT OF JAVANESE GINSENG MUCILAGE AND ORANGE OIL CONCENTRATIONS ON PROPERTIES AND OXIDATIVE STABILITY OF BEVERAGE EMULSIONS*** **50-63**
- Iancu Maria Lidia; *COMPARATIVE ANALYSIS OF THE QUALITY INDICATORS OF ORANGE JUICE OBTAINED BY DIFFERENT EXTRACTION METHODS*** **64-78**
- Linh T.K. Vu, Phu Quang Pham, Dao Thi Anh Phan, Dzung Tan Nguyen; *BUILDING AND SOLVING THE MATHEMATICAL MODEL OF TRANSIENT HEAT TRANSFER DURING THE PEANUT ROASTING PROCESS TO DETERMINE THE ROASTING PARAMETERS*** **79-88**
- Hamza Alaşalvar, Bülent Başıyigit, Duygu Aslan Türker, Necattin Cihat İçyer, Mustafa Çam; *POMEGRANATE SEED OIL: EXTRACTION, SHELF LIFE PREDICTION, AND MICROENCAPSULATION*** **89-102**
- Kabiri G., Haddioui A., Bouda S.; *MOROCCAN WALNUT ACCESSIONS RESEARCH USING MORPHOLOGICAL, BIOCHEMICAL AND MOLECULAR ANALYSES*** **103-113**
- Sony George, Anish Thomas, Praveen Kumar Ghodke, Malladi V Pavan Kumar; *OPTIMIZATION OF SPRAY DRYING FOR COCONUT MILK POWDER*** **114-128**

USING RESPONSE SURFACE METHODOLOGY AND INVESTIGATION OF THE POWDER PROPERTIES

Anna Dorohova, Aleksandr Basov, Arkady Moiseev, Stepan Dzhimak; 129-139
DETERMINATION OF CONCENTRATIONS 2H AND 17O BY NMR SPECTROSCOPY METHOD IN DRINKING WATER, FRUIT AND VEGETABLES FRESH JUICES WITH INTRODUCTION OF EU(CF₃SO₃)₃ TO THE REFERENCE SAMPLE

Abir Nouioua, Abdelouahab Benseddik, Colette Besombes, Karim Allaf, 140-159
Abdelbaki Benmounah, Adiba Benahmed Djilali; *NUTRACEUTICALS COMPOUNDS EXTRACTION OPTIMIZATION FROM OPEN AIR AND SWELL-DRIED BANANA PEEL POWDERS*

Mustofa Ahda, Irwandi Jaswir, Deni Subara; 160-167
ENHANCEMENT OF PHYSICAL PROPERTIES OF GELATIN-BASED FILM BY BOVINE SERUM ALBUMIN

Ilesanmi, J.O.Y., Hussein, J.B., Falope, O.J. and Filli, K.B.; 168-179
IMPACTS OF PRETREATMENTS AND DRYING TECHNIQUES ON THE PHYSIOCHEMICAL, MICROBIAL, AND SENSORY PROPERTIES OF WHITE YAM (Dioscorea Rotundata) FLOUR

Nikolay Delchev Kolev, Desislava Borislavova Vlahova-Vangelova, Desislav 180-188
Kostadin ov Balev, Stefan Georgiev Dragoev; *STABILIZATION OF OXIDATIVE PROCESSES IN COOKED SAUSAGES BY OPTIMIZATION OF INCORPORATED BIOLOGICALLY ACTIVE SUBSTANCES*

Bornu Kabolobari Barielnu, Beyza Hatice Ulusoy, Halil Doruk Kaynarca; 189-200
DRINKING WATER MICROBIOLOGY: DESIRED AND UNDESIRED MICROBIOTA, LEGISLATION, OUTBREAKS AND ANALYSIS

Çağla Pınarlı, Fatih Tarlak; 201-215
MICROORGANISMS RESPONSIBLE FOR DETERIORATION OF FOOD PRODUCTS: REVIEW

Razieh Shahbazi, Behrouz Akbari Adergani, Nabi Shariatifar, Khadijeh 216-233
Jafari, Ensiyeh Taheri, Ayub Ebadi Fathabad, Naiema Vakili Saatloo, Ebrahim Molaee Aghaee, Parisa Sadighara, Amin Mousavi Khaneghah; *ASSESSMENT OF FOOD ADDITIVES IMPACT ON ACRYLAMIDE FORMATION IN POPCORN SUPPLIED IN TEHRAN, IRAN: A RISK ASSESSMENT STUDY*



ENHANCEMENT OF PHYSICAL PROPERTIES OF GELATIN-BASED FILM BY BOVINE SERUM ALBUMIN

Mustofa Ahda^{1,2,6✉}, Irwandi Jaswir^{1,5}, Deni Subara^{3,4}

¹Department of Pharmacy, Faculty of Pharmacy, Universitas Ahmad Dahlan, Yogyakarta

²Ahmad Dahlan Halal Center, Universitas Ahmad Dahlan, Yogyakarta

³Department of Agricultural Industrial Technology, Institut Teknologi Sumatera (ITERA)

⁴Department of Biotechnology Engineering, International Islamic University Malaysia, Kuala Lumpur Malaysia

⁵INHART, International Islamic University Malaysia, Kuala Lumpur, Malaysia

⁶Department of Pharmaceutical Chemistry, International Islamic University Malaysia, Kuantan Malaysia

✉mustofa_ahda@yahoo.com

<https://doi.org/10.34302/crpjfst/2022.14.4.12>

Article history:

Received

21 September 2021

Accepted

22 July 2022

Published

December 2022

Keywords:

Gelatin-based film;

Hydrogen bonding;

Glass transition;

Optimum of BSA/gelatin ratio.

ABSTRACT

Biopolymer-based films are created from plant or animal materials such as carbohydrates and proteins. In this study, a biopolymer-based film from gelatin and Bovine Serum Albumin (BSA) was created to form a film through cross-linking interaction of both biopolymers. The synthesized biopolymer film was characterized using Differential Scanning Calorimetry (DSC), Scanning Electron Microscopy (SEM), and Fourier Transform Infrared (FTIR) as morphological evaluation. Besides, the encapsulation efficiency of BSA-gelatin blend film was also evaluated. The coagulation process was performed using acetone carried out at 35 °C for 4 hours under stirring. The formed particles were separated from the solution using high centrifugation around 12,000 rpm for 30 min and then kept at -80 °C.

Based on the FTIR spectra showed that BSA and gelatin have the same functional group such as hydroxyl (OH) and Amino I, II, and III which appear at 3278 cm⁻¹, 1633 cm⁻¹, 1542 cm⁻¹, and 1241 cm⁻¹, respectively. After linkage reaction, the gelatin-BSA interaction created more strength interaction that caused no vibration functional groups seen. It also increased glass transition temperature where the resulted melting point of gelatin-based and 70% BSA/gelatin-based films are 152.2 and 260 °C, respectively. The encapsulated BSA in the blend film reached above 90% in the BSA/gelatin ratio of 70%.

1.Introduction

In the last decade, nanotechnology is a fascinating field that was interested some researchers. The expansion of nanotechnology eventually is considered in this stage because it possesses various advantages and is favorable in some industry fields. Hence, some products were designed via nanotechnology, including nanofibers (Jeong and Park, 2014; Panzalvota et. al., 2014) and nanocomposites (Umamaheswari et. al., 2015; Premalatha and Kothai, 2015; Satapathy et. al, 2017).

One of the raw materials commonly used and interested by the researcher is gelatin. Gelatin has been exploited and developed via nanotechnology to be converted to nanomaterial products, named; gelatin nanoparticles (GNPs). The application of gelatin is mostly used in several products beneficial to drugs delivery system (Fook and Liberman, 2015), as well as delivery of protein including Bovine Serum Albumin (BSA) and Human Serum Albumin (HSA) (Kaintura et al., 2015), and as food

packaging potential (Hanani et al., 2014), and hard and soft capsule (Prasad, 2017).

The application of gelatin as a macromolecule transport, including protein delivery models, produces many advantages because it can protect from protein degradation and control the release time (Thakur et al, 2013). Besides, the application of gelatin nanoparticles also increases the bioavailability of the drug (Azimi et al, 2014). Gelatin applications are also a proficient carrier for large or small molecules (Jahanshahi and Babaei, 2008).

The gelatin application as a protein delivery system has been carried out and reported by several studies. Azimi et al. (2014) reported that gelatin from bovine skin is used as BSA delivery using a two-step desolvation method. The encapsulated BSA into gelatin nanoparticles using the water/oil (w/o) emulsion method has an average particle diameter is 840 nm (Li et al, 1998). The study from Azimi et al. (2014) showed that encapsulated BSA into gelatin nanoparticles using a two-step desolvation method resulted in a particle size around 200-300 nm. This study is not applying gelatin nanoparticles as a delivery system of BSA but it is focused on the evaluation of the biopolymer gelatin-based and BSA/gelatin-based film that is able to support the application of food packaging or hard and soft capsule. A previous study by Panzavolta et al., (2014) created gelatin-based film with a simple method.

2. Materials and methods

2.1. Synthesis of Blend Film from BSA and Gelatin

The synthesis of BSA-gelatin-based film follows the research from Sailaja and Amareshwar (2012) with slight modification. Gelatin nanoparticles were synthesized using acetone as a desolvating agent via a one-step desolvation method. 1 g of hydrolyzed gelatin was dissolved with 10 mL aquades and heated at 35°C for 5 min. The pH of the gelatin solution was adjusted around pH range 2.5-3 using HCl 0,1 N and then heated at 35°C for 5 min. After that, 25 mL of the acetone solution was added to the gelatin solution dropwise for 10 min. In the

last step, this solution was added with 500 uL glutaraldehyde 8% and stirred for 4 hours until raising the particles. To obtain the gelatin nanoparticles from the solution was separated using centrifugation at 1000 rpm for 30 min. Afterward, the gelatin nanoparticles were dried to get the solid form. The encapsulation process of BSA level into gelatin nanoparticles is performed using a similar method with gelation nanoparticles producing. BSA/gelatin ratio used is between 0-100%.

2.2. The Entrapment Calculation of Bovine Serum Albumin (%) into Blend Film

The entrapped procedure of BSA into gelatin nanoparticles was determined using a spectrophotometer at $\lambda = 278$ nm (Azimi et al, 2014). The unloading of BSA was used to calculate the encapsulation efficiency (EE, %) using the equation:

$$EE (\%) = [(total \text{ BSA added} - \text{amount of free BSA}) / total \text{ BSA added}] \times 100. \quad (1)$$

2.3. Characterization of gelatin nanoparticles

The characterization of the gelatin nanoparticle products was analyzed using Scanning Electron Microscopy (SEM) (Phenom Pro X) to detect the morphology of the nanoparticles and Differential Scanning Colorimetry (DSC) (1-STARe, Mettler Toledo, Columbus, OH) to characterize the melting point of gelatin nanoparticle resulted. The Fourier Transform Infrared (FTIR) (Perkin Elmer) was used to detect the functional group vibrations of nanoparticle products.

3. Results and discussions

3.1. Identification of Interaction between BSA and Gelatin using FTIR

The gelatin-based film was synthesized using the one-step desolvation method because it is a more simple and convenient method. This method is able to encapsulate biopolymer is approximately 99% (Wang et al., 2018) and can produce stable gelatin nanoparticles in ranging small particle sizes of around 200-300 nm

(Mohanty and Bohidar, 2003; Azimi et al., 2014). BSA/gelatin-based film is a new material because the previous research was focused on the application of gelatin as a BSA delivery system. Both gelatin and BSA are composed of different protein monomers. The amino acid levels in gelatin are glycine of 33%; Proline of 21%; Hydroxyproline of 10%, and X (other amino acid monomers) of around ~36% (Djabourov, et al., 1988; Yasmin et al., 2017). While the amino acids of BSA are Lysine, Threonine, Valine, Leucine, Isoleucine, Tryptophan, Histidine, Methionine, Methionine + Cysteine, Tyrosine, Phenylalanine, Phenylalanine + Tyrosine, Aspartic acid, Serine, Glutamic acid, Proline, Glycine, Alanine, and Arginine (Prata and Sgarbieri, 2008).

To evaluate the chemical interaction between gelatin and BSA in blend film can be seen in Figure 1. Figure 1 described that BSA possesses the vibration fields in 3278 cm^{-1} as a hydroxyl (OH) stretching or NH_2 stretching vibration (Amide A) (Qiu et al., 2019). The vibration of C-H alkane arises of around 2972 cm^{-1} and the supported other wavenumbers at 1538 cm^{-1} and 1454 cm^{-1} as CH_3 and CH_2 vibration, respectively (Figure 2). Besides, the wavenumber at 2972 cm^{-1} also illustrates the vibration asymmetric of Amide B as free $-\text{NH}^{3+}$ from lysine or terminated N (Yang et al., 2019). While the functional group vibration at 1633 cm^{-1} , 1542 cm^{-1} , and 1241 cm^{-1} indicate molecule vibrations from amide groups such as amide I, amide II, and amide III (Kaintura et al., 2015; Yang et al., 2019).

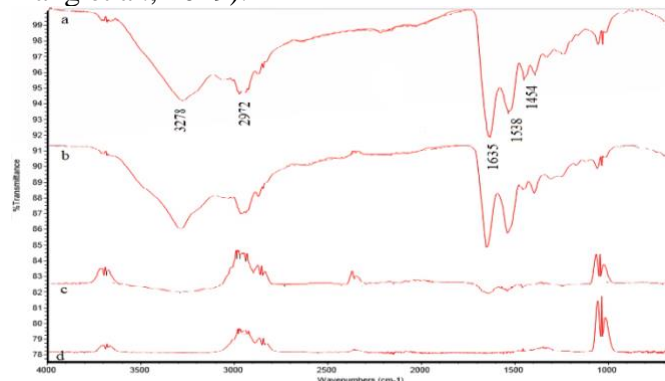


Figure 1. FTIR Spectrum from; a. BSA ; b. Hydrolyzed Gelatin; c. Gelatin-based film; d. 70% BSA/gelatin-based film

The blended gelatin-BSA film and gelatin film have changed the vibrations of functional groups. Previous research from Kaintura et al., (2015) reported that the indication of protein encapsulated into gelatin nanoparticles would change their vibrations and decrease FTIR intensity. However, the gelatin nanoparticles involve intermolecular interaction through hydrogen bonds. It caused the vibration of functional groups in the gelatin structure to be unable to vibrate freely. Therefore, the intensity of the FTIR spectrum of gelatin nanoparticles has decreased significantly compared with gelatin structure (Figure 1). It is also seen in the blended gelatin-BSA as an indication that BSA functional group also interacts with gelatin functional groups forming a rigid molecule.

3.2. Melting point of BSA/Gelatin-based Film

The rigidity of BSA/gelatin-based film had influenced the melting point of the material. DSC analysis also reveals differences in melting point transposition between gelatin nanoparticles and BSA encapsulated into gelatin nanoparticles. Both particles have been observed that the melting point of the gelatin-based film is an exothermic peak of about 152.20°C , while BSA encapsulated into the gelatin-based film is able to increase the melting points which is an exothermic peak of around 201.43°C (Figure 2).

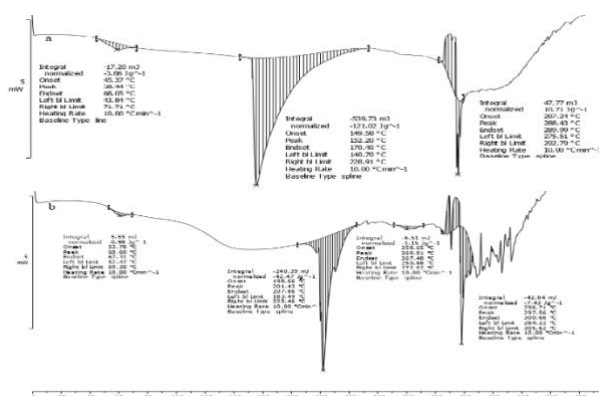


Figure 2. The Result of Differential Scanning Colorimetry (DSC) of nanoparticle; a. Gelatin-based film; b. 70% BSA/gelatin-based film

Based on this result, the interaction of BSA with gelatin is able to build a rigid structure, it can occur through the inclusion of complex interaction between BSA and gelatin causing its melting point to increase significantly. Yasmin et al., (2017) explained that mechanical properties of gelatin nanoparticles covering thermal properties and water swelling ability were significantly affected by the interaction gelatin formation, especially in complex biopolymers. Previous research reported several characteristics of the material applied for edible plasticizer film excipients (Table 1).

Table 1 explained that the development of blended polymers can improve their physical properties and quality. Occasionally, they can be fabricated as phenolic-polymeric hybrids in nutraceutical and drugs delivery systems, edible films, hydrogels, and nanoparticles (Liu et al.,

2019). One of the features evaluated for the polymeric-based film is the T_g value (Liang et al., 2019). The T_g value indicates generally to amorphous structure or semicrystalline materials formed (Hoque et al., 2011; Acevedo et al., 2014), while the T_m value is related to the dissociation of hydrogen bond and polymers chains cleavage occur (Cai et al., 2019). The result of this study showed that the gelatin-BSA composite can increase the T_g value indicating both polymers interact strongly. The intermolecular reaction of both polymers will increase of T_g value (Hosseini et al., 2013), indicating that the moisture content in the matrix decreased (Avecedo et al., 2014). This phenomenon will affect other physical and mechanical properties of the materials. The rigidity of this film was also seen in SEM analysis (Figure 3).

Table 1. The development of blended polymeric as edible film material

Polymeric Agent 1	Polymeric Agent 2	Physical Properties	Applications	References
Chitosan	Gelatin	T_g (gelatin): 50.6°C, T_m : 69.6 °C T_g (gelatin-chitosan): 51.1°C, T_m : 75.0°C	Biofilm	Acevedo et al., 2014
Chitosan	Gelatin	T_g (gelatin-chitosan): 56.18°C	Edible film	Cai et al., 2019
Chitosan	Fish gelatin	T_g (gelatin): 29.8°C T_g (chitosan): 56.1°C T_g (gelatin-chitosan): 55.9°C	Edible film	Hosseini, et al., 2013
Chitosan	Cellulose	T_g (chitosan): 91.03°C T_g (chitosan-cellulose): 91.33°C	Biofilm	Liang et al., 2019
Chitosan	HPMC	T_g (chitosan): 114.06°C T_g (HPMC): 164.56°C T_g (chitosan-HPMC): 196.23°C	Edible film	Rotta et al., 2011
Chitosan	Methyl Cellulose	T_m (chitosan): 118°C T_m (methyl cellulose): 115°C T_m (chitosan-methyl cellulose): 110°C	Edible film	Rachtanapun and Wongchaiya, 2012
Gelatin	-	T_g (gelatin): 60 °C, T_m : 214,02°C	Biofilm	Perkasa et al., 2013
Gelatin	MPI	T_g (gelatin): 33.70°C T_g (MPI): 22.83°C T_g (gelatin-MPI): 30.08°C	Edible film	Hoque et al., 2011
Gelatin	PVA	T_g (gelatin-PVA): 43-53°C, T_m : 98.5-138.9°C	Edible film	Sobral et al., 2011
Gelatin	BSA	T_g (gelatin): 58.44 °C, T_m : 152.20°C T_g (gelatin-BSA): 60.60°C, T_m : 201.43°C	Potential for edible film and hard capsule	This work

PVA: Poly Vinyl Alcohol; HPMC: hydroxypropylmethylcellulose; MPI: mungbean protein isolate

Tg: glass transition temperature, Tm: melting temperature

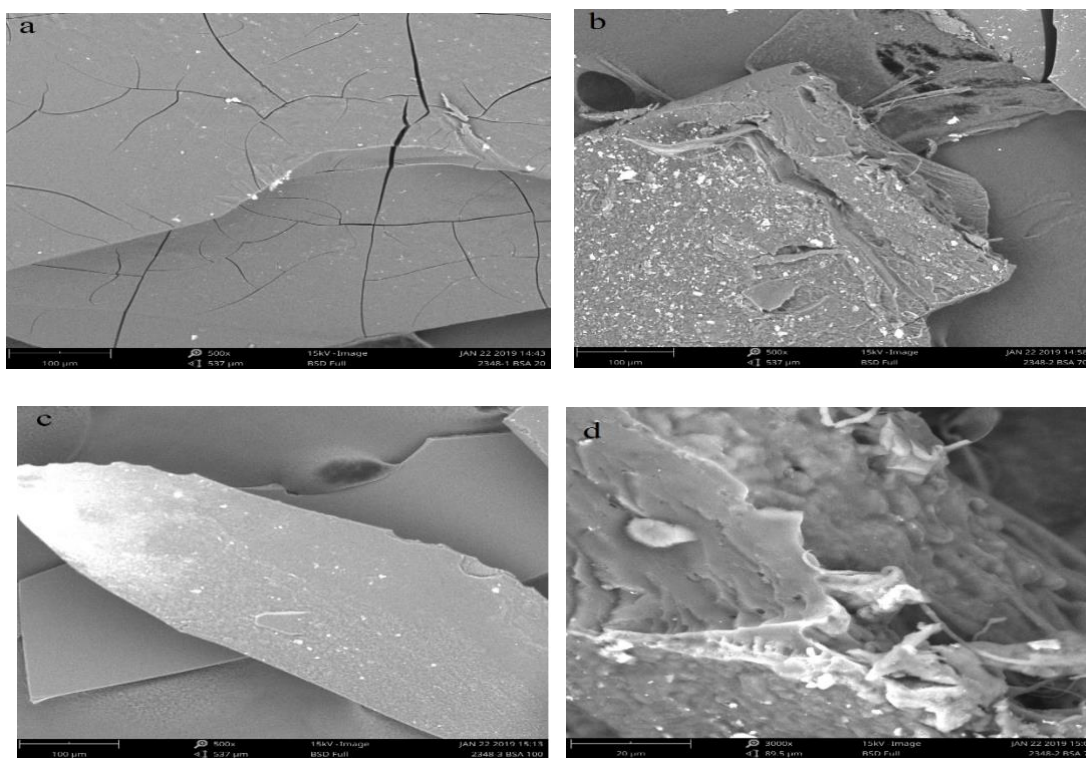


Figure 3. Scanning Electron Microscopy of Different of BSA Concentration loaded into Gelatin-based film; a. 20 % (w/w) BSA; b. 70% (w/w) BSA; c. 100% (w/w) BSA (all scale pictures were seen at 100 μm) and, d. 70% BSA (scale picture was seen at 20 μm)

3.3. Morphology analysis of gelatin-based film using SEM

Based on figure 3. the effect of BSA concentration affected the different morphology of the produced gelatin-based film. The use of 20% BSA loaded into gelatin-based film generate particle properties that have easily cracked. Whereas the 70% BSA and 100% BSA can create a rigid material and a smooth material, respectively. Even the 70% BSA in gelatin-based film produces strong fibers (figure 3b and 3d). This fiber is an aggregate of spherical shape from gelatin nanoparticles because of the temperature conditions in the gelatin-based film processing. Besides, the suggestion of this study is to use a 70% BSA/gelatin ratio in the production of BSA/gelatin-based film because gelatin-based film can encapsulate the optimum of BSA concentration in 50-70% BSA/gelatin ratio up to more than 90% (Figure 4). The encapsulation efficiency (EE) resulted was similar to previous research from Kaintura et al., (2015) reported

that the encapsulation efficiency of Bovine Serum Albumin (BSA) and Human Serum Albumin (HSA) into gelatin nanoparticles which is 90% and 80%, respectively. Meanwhile, Azimi et al., (2014) also explained that the two-step desolvation method can produce a particle size range of gelatin nanoparticles of 200-300 nm with entrapment efficiency of BSA reached 87.4%. Based on this result, these physical properties are supporting the use of modified materials as edible plasticizer film excipients or hard capsule materials. However, the blended gelatin-BSA is also applied as a soft capsule or an edible plastic because BSA creates smooth material in a high BSA/gelatin ratio.

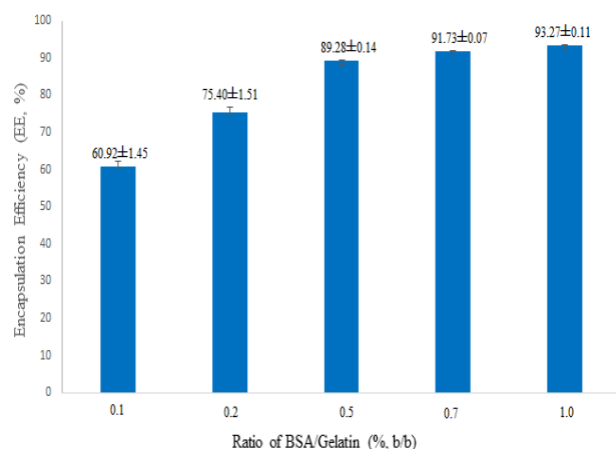


Figure 4. Encapsulation Efficiency (EE) of BSA Loaded into Gelatin-based film

4. Conclusions

The encapsulated BSA into gelatin nanoparticles affects several properties of the material including vibration of functional groups, melting point, and physical properties. The BSA/gelatin ratio of 70% produced a strong fiber that is agglomerating with other fiber become a solid material and the encapsulation efficiency reached above 90%. Based on this research, the effect of the encapsulated BSA into gelatin nanoparticles can improve material properties, including rigid characteristics and melting point. Therefore, it may be applied as edible plasticizer film excipients.

5. References

Abdala, K. F., Kamoun, E. A., and El Maghraby, G. M. 2015. Optimization of the entrapment efficiency and release of ambroxol hydrochloride alginate beads, *Journal of Applied Pharmaceutical Science*, 5 (04), 013-019, DOI: 10.7324/JAPS.2015.50403

Acevedo, C. A., Díaz-Calderón, P., López, D., & Enrione, J. (2014). Assessment of gelatin–chitosan interactions in films by a chemometrics approach. *CyTA - Journal of Food*, 13(2), 227-234. doi:10.1080/19476337.2014.944570

Azimi, B., Nourpanah, P., Rabiee, M., and Arbab, S. 2014. Producing Gelatin nanoparticles as Delivery System for Bovine

Serum Albumin, *Iran Biomed J.* 18(1), 34–40. doi: [10.6091/ibj.1242.2013]

Cai, L., Shi, H., Cao, A., & Jia, J. (2019). Characterization of gelatin/chitosan ploymer films integrated with docosaheanoic acids fabricated by different methods. *Scientific Reports*, 9(1). doi:10.1038/s41598-019-44807-x

Djabourov, M., Leblond, J., and Papon, P. 1988. Gelation of aqueous gelatin solutions. I. Structural investigation. *Journal de Physique*, 49 (2), 319-332. doi: 10.1051/jphys:01988004902033300

Foxx, M., and Zilberman, M. 2015. Drug delivery from gelatin-based systems, *Expert Opinion on Drug Delivery*. 12(9), 1547-1563. doi: 10.1517/17425247.2015.1037272

Hanani, Z. A. N., Roos, Y. H., and Kerry, J. P. 2014. Use and Application of Gelatin as Potential Biodegradable Packaging Materials for Food Products, *International journal of biological macromolecules*. 71, 94-102. <https://doi.org/10.1016/j.ijbiomac.2014.04.027>

Hoque, M. S., Benjakul, S., Prodpran, T., & Songtipya, P. (2011). Properties of blend film based on cuttlefish (*Sepia pharaonis*) skin gelatin and mungbean protein isolate. *International Journal of Biological Macromolecules*, 49(4), 663–673. doi:10.1016/j.ijbiomac.2011.06.028

Hosseini, S. F., Rezaei, M., Zandi, M., & Ghavi, F. F. (2013). Preparation and functional properties of fish gelatin–chitosan blend edible films. *Food Chemistry*, 136(3-4), 1490–1495. doi:10.1016/j.foodchem.2012.09.081

Jahanshahi, M., and Babaei, Z. 2008. Protein nanoparticle: A unique system as drug delivery vehicles, *African Journal of Biotechnology*. 7(25), 4926-4934

Jeong, L., and Park, W. H. 2014. Preparation and Characterization of Gelatin Nanofibers Containing Silver Nanoparticles, *Int. J. Mol. Sci.* 15, 6857-6879. doi:10.3390/ijms15046857

- Kaintura, R., Sharma, P., Sigh, S., Rawat, K., Solanki, P. R. 2015. Gelatin nanoparticles as a Delivery System for Proteins, *J Nanomed Res.* 2(1): 1-3, doi: 10.15406/jnmr.2015.02.00018.
- Liang, J., Wang, R., & Chen, R. (2019). The Impact of Cross-linking Mode on the Physical and Antimicrobial Properties of a Chitosan/Bacterial Cellulose Composite. *Polymers*, 11(3), 491. doi:10.3390/polym11030491
- Li, J. K., Wang, N., Wu, X. S. 1998. Gelatin nanoencapsulation of protein/peptide drugs using an emulsifier-free emulsion method, *J Microencapsul.* 15(2): 163-72. doi:10.3109/02652049809006846
- Liu, J., Yong, H., Yao, X., Hu, H., Yun, D., & Xiao, L. (2019). Recent advances in phenolic–protein conjugates: synthesis, characterization, biological activities and potential applications. *RSC Advances*, 9(61), 35825–35840. doi:10.1039/c9ra07808h
- Mohanty, B., and Bohidar, H. 2003. Systematic of alcohol-induced simple coacervation in aqueous gelatin solutions. *Biomacromolecules*. 4, 1080–1086.
- Panzavolta, S., Bracci, B., Gualandi, C., Focarete, M. L., Treossi, E., Kouroupis-Agalou, K., Rubini, K., Bosia, F., Brely, L., Pugno, N. M., Palermo, V., Bigi, A. 2014. Structural reinforcement and failure analysis in composite nanofibers of graphene oxide and gelatin, *Carbon*. 78, 566–577. doi: 10.1016/j.carbon.2014.07.040
- Perkasa, D. P., Erizal, Darwis D., and Rosyid, A. 2013. Effect of Gamma Irradiation on Mechanical and Thermal Properties of Fish Gelatin Film Isolated from Lates Calcarifer Scales, *Indo. J. Chem.*, 13 (1), 28 – 35. doi: 10.22146/ijc.21322
- Prasad, V. D. 2017. Formulation and modifying drug release from Hard and Soft Gelatin Capsules for Oral drug delivery, *Int. J. Res. Dev. Pharm. L. Sci.* 6 (4): 2663-2677. [http://dx.doi.org/10.21276/IJRDPL.227_8-0238.2017.6\(4\).2663-2677](http://dx.doi.org/10.21276/IJRDPL.227_8-0238.2017.6(4).2663-2677)
- Prata, A. S., and Sgarbieri, V. C. 2008. Composition and physicochemical properties of two protein fractions of bovine blood serum, *Ciênc. Tecnol. Aliment.*, Campinas, 28(4), 964-972.
- Premlatha, T. S and Kothai, S. 2015. Synthesis, Characterization and Antibacterial Activity of Gelatin-Herb Nanocomposite, *Asian Journal of Biomedical and Pharmaceutical Sciences*. 5(50), 2015,34-36. doi: 10.15272/ajbps.v5i50.752
- Qiu, Y. T., Wang, Y. M., Yang, X. R., Zhao, Y. Q., Chi, C. F., and Wang, B. 2019. Gelatin and Antioxidant Peptides from Gelatin Hydrolysate of Skipjack Tuna (*Katsuwonus pelamis*) Scales: Preparation, Identification and Activity Evaluation. *Marine Drugs*, 17(10), 565, 1-17. doi:10.3390/md17100565
- Rachtanapun, P., and Panchat Wongchaiya, P. 2012. Effect of Relative Humidity on Mechanical Properties of Blended Chitosan-Methylcellulose Film, *Chiang Mai J. Sci.*, 39(1), 133-137.
- Rotta, J., Minatti, E., & Barreto, P. L. M. (2011). Determination of structural and mechanical properties, diffractometry, and thermal analysis of chitosan and hydroxypropylmethylcellulose (HPMC) films plasticized with sorbitol. *Ciência e Tecnologia de Alimentos*, 31(2), 450–455. doi:10.1590/s0101-20612011000200026
- Sailaja, A. K., and Amareshwar, P. 2012. Preparation of BSA Nanoparticles by Desolvation Technique Using Acetone as Desolvating Agent, *Internasional journal of Pharmaceutical Sciences and Nanotechnology*. 5(1), 1643-1647
- Satapathy, M. K., Chiang, W. H., Chuang, E. Y., Chen, C. H., Liao, J. L., and Huang, H. N. 2017. Microplasma-assisted hydrogel fabrication: A novel method for gelatin-graphene oxide nano composite hydrogel synthesis for biomedical application, *PeerJ*. 5,e349. doi 10.7717/peerj.3498
- Sobral, P. J. A., de Carvalho, R. A., Moraes, L. C. F., Bittante, A. M. Q. B., and Monterrey-Quintero, E. S. 2011. Phase transitions in

- biodegradable films based on blends of gelatin and poly (vinyl alcohol), *Ciênc. Tecnol. Aliment.*, Campinas, 31(2), 372-379
- Thakur, G., Rouseau, D., and Rafanan, R. 2013. Chapter 3: Gelatin based matrices for drug delivery applications, *Gelatin: Production, Applications and Health Implications*, Nova Science Publishers, 49-70, ISBN 978-1-62417-627-2
- Umamaheswari, G., Sanuja, S., John, V. A., Kanth, S. V., and Umapathy, M. J. 2015. Preparation, Characterization and Anti-Bacterial Activity of Zinc Oxide-Gelatin Nanocomposite Film for Food Packaging Applications, *Polymers & Polymer Composites*. 23(3), 199-204
- Wang, B., Akanbi, T. O., Agyei, D., Holland, B. J., and Barrow, C. J. 2018. Coacervation Technique as an Encapsulation and Delivery Tool for Hydrophobic Biofunctional Compounds. *Role of Materials Science in Food Bioengineering*, 235–261.
doi:10.1016/b978-0-12-811448-3.00007-3
- Yang, X. R., Zhao, Y. Q., Qiu, Y. T., Chi, C. F., and Wang, B. 2019. Preparation and Characterization of Gelatin and Antioxidant Peptides from Gelatin Hydrolysate of Skipjack Tuna (*Katsuwonus pelamis*) Bone Stimulated by in vitro Gastrointestinal Digestion. *Marine Drugs*. 17(2), 78.
doi:10.3390/md17020078
- Yasmin, R., Shah, M., Khan, S. A., and Ali, R. 2017. Gelatin nanoparticles: a potential candidate for medical applications. *Nanotechnology Reviews*, 6(2), 1-17.
doi:10.1515/ntrev-2016-0009

Acknowledgment

The Authors give gratefulness to Universitas Ahmad Dahlan and International Islamic University Malaysia (IIUM) for supporting all facilities in this research. We are proud to work in the Engineering Department's Biotechnology Laboratory at IIUM.